

# RecyClass

## RECYCLABILITY EVALUATION PROTOCOL

### FOR PS CONTAINERS

STANDARD LABORATORY PRACTICE  
REP-PS-01

# RecyClass

## CONTENT

CONTENT .....	2
GLOSSARY .....	3
1. INTRODUCTION AND PURPOSE OF THE PROTOCOL .....	5
2. SCOPE OF THE PROTOCOL .....	6
3. DISCLAIMER .....	6
4. LABORATORY TESTING METHODOLOGY .....	6
4.1 CONTROL SAMPLE SELECTION .....	8
4.2 VIRGIN SAMPLE SELECTION .....	8
5. LABORATORY TEST PROCEDURES .....	9
5.1 PRE-TREATMENT STEPS .....	9
5.1.1 GRINDING .....	9
5.1.2 WASHING .....	9
5.1.3 SEPARATION BY DENSITY .....	9
5.1.4 DRYING .....	11
5.1.5 AIR ELUTRIATION .....	11
5.2 EXTRUSION .....	11
5.2.1 FLAKE BLENDS PREPARATION .....	11
5.2.2 FLAKE BLENDS COMPOSITION .....	12
5.2.3 PELLET PRODUCTION .....	12
5.3 CONVERTING .....	15
5.3.1 INJECTION MOULDING .....	15
5.3.2 SHEET EXTRUSION .....	16
DOCUMENT VERSION HISTORY .....	19
ANNEX I – CONTROL SAMPLES SELECTION .....	20
ANNEX 2 – MFI RANGE FOR CONTROL SAMPLE (OPTION 2) .....	21

## GLOSSARY

<b>A.0</b>	100 % control flakes
<b>A.25</b>	Blend 75/25 control/innovation flakes
<b>A.50</b>	Blend 50/50 control/innovation flakes
<b>A.100</b>	Blend 100 % innovation flakes
<b>ASTM</b>	American Society for Testing and Materials
<b>B.0</b>	Sheet made of 50 % of virgin pellets and 50 % of B.0 pellets
<b>B.25</b>	Sheet made of 50 % of virgin pellets and 50 % of B.25 pellets
<b>B.50</b>	Sheet made of 50 % of virgin pellets and 50 % of B.50 pellets
<b>B.100</b>	Sheet made of 50 % of virgin pellets and 50 % of B.100 pellets
<b>Control Sample</b>	Plain PS container (or PS resin that has already been thermally processed once) used as benchmark
<b>C.0</b>	Plaque made of 100 % control pellets
<b>C.25</b>	Plaque made of 75 % control and 25 % innovation pellets
<b>C.50</b>	Plaque made of 50 % control and 50 % innovation pellets
<b>C.100</b>	Plaque made of 100 % innovation pellets
<b>EN</b>	European Standard
<b>Innovation Sample</b>	Container containing the innovative technology
<b>ISO</b>	International Organization for Standardization
<b>MFI</b>	Melt Flow Index
<b>PS</b>	Polystyrene
<b>PVC</b>	Polyvinyl Chloride
<b>TC</b>	Technical Committee
<b>TGA</b>	Thermogravimetric Analysis
<b>Virgin Material</b>	PS resin that will for the first time be converted to a plastic product (no thermal pre-treatment)
<b>wt%</b>	Weight Percentage

# RecyClass

## DISCLAIMER

“RecyClass is a non-profit, cross-industry initiative advancing recyclability, bringing transparency to the origin of plastic waste and establishing a harmonized approach toward recycled plastic calculation & traceability in Europe. The Recyclability Evaluation Protocols promote recyclability by encouraging the industry to test new plastic technologies, materials or products, providing recommendations on improving their recyclability before market launch.

The Recyclability Evaluation Protocols are freely available to download on the [RecyClass website](#). Companies developing new plastic packaging concepts are encouraged to use them to self-assess the impact of their solutions on recyclability and highlight potential issues. **However, compliance with a Recyclability Evaluation Protocol is not a replacement for an official assessment and may not be used as a marketing tool.** The RecyClass Steering Board, following the recommendations of the Technical Committees, will decide on the compatibility of the innovation with recycling according to the evaluation results, granting Recyclability Approval Letter to the Applicant.

All tests must follow the Evaluation Protocols recommended by the RecyClass Technical Committees and must be conducted by an independent laboratory recognised by RecyClass which has no legal affiliation to the applicant.

More information is reported in the RecyClass Internal Procedures, available on the [RecyClass website](#).

# RecyClass

## 1. INTRODUCTION AND PURPOSE OF THE PROTOCOL

The “RecyClass<sup>1</sup> Recyclability Evaluation Protocol for PS Containers” referred to in this document as “The Protocol” describes the methodology the applicant must follow at a laboratory scale to determine if a plastic packaging innovation is compatible with the post-consumer PS recycling stream. The Protocol targets companies responsible for introducing a packaging product onto the market. The applicant shall proceed with the Protocol as established in the Assessment Process for Applicants of Recyclability Evaluation in the RecyClass Internal Procedures<sup>2</sup> and RecyClass Recyclability Approval Quality Management & Procedures document<sup>3</sup>.

The Protocol analyses whether an innovation will undergo the necessary pre-treatment, extrusion and conversion steps described in this methodology at a laboratory scale without negatively impacting the recycling process and the quality of the recycled PS material. It aims to prove the recyclability<sup>4</sup> of plastics packaging while encouraging innovation in the PS market. The overall goal is to maintain the protection of packaged goods and their marketing display functions without obstructing the proper functioning of the PS recycling process and ensuring the highest possible quality of the recycled HDPE.

This document provides guidance on the testing methodology that shall be followed, including benchmark recommendations to guide the interpretation of the results.

PS terminology as it is used in this document, refers to rigid plastic containers predominantly used for yogurt pots and other food and beverage products, except XPS and EPS.

Please note that all units in this protocol are expressed following The International System of Units<sup>5</sup>, from the Bureau International des Poids et Mesures.

---

<sup>1</sup> RecyClass assesses the recyclability of a plastic package providing a ranking from A to C. RecyClass also provides specific indications and recommendations on how to improve packaging design to fit current recycling technologies. More information at <https://recyclclass.eu/>

<sup>2</sup> [RecyClass Internal Procedures](#)

<sup>3</sup> [RecyClass Technology Approval Quality Management & Procedures](#)

<sup>4</sup> Recyclability definition according to PRE & APR: Plastics must meet four conditions for a product to be considered recyclable: 1. The product must be made with a plastic that is collected for recycling, has market value and/or is supported by a legislatively mandated program. 2. The product must be sorted and aggregated into defined streams for recycling processes. 3. The product can be processed and reclaimed/recycled with commercial recycling processes. 4. The recycled plastic becomes a raw material that is used in the production of new products.

<sup>5</sup> [SI Brochure - BIPM](#)

## 2. SCOPE OF THE PROTOCOL

The scope of the Protocol covers any innovation introduced to the existing packaging solutions for PS. Before initiating the evaluation, the applicant shall review the Design for Recycling Guidelines for PS containers<sup>6</sup> to confirm that the PS innovation is compatible with the recycling stream for PS containers.

1. The scope of this Protocol covers the following non-exhaustive list of packaging solutions and/or innovations: PS resins
2. Barrier materials
3. Mineral fillers and additives that increase or decrease the density of PS packaging
4. Non-PS closure systems
5. Non-PS liners, seals, and valves
6. Non-PS labels and sleeves
7. Adhesives
8. Inks

Following the RecyClass Recyclability Methodology<sup>7</sup>, packaging containing aluminium, metal, foam, degradable plastics, black carbon surface, as well as PVC and PVDC layers are considered as disqualifying criteria for recyclability. Consequently, packaging containing any of these features does not fall under the scope of this Protocol.

## 3. DISCLAIMER

The Protocol is created to represent as accurately as possible how the current PS recycling process works at an industrial scale. RecyClass PS Technical Committee reserves the right for further testing if necessary, to issue a final opinion on the recyclability of the tested innovation.

Within RecyClass, “easy-to-empty” and “easy-to-access” indexes are essential factors when considering the recyclability of a package. At the state-of-the-art, at PS mechanical recycling facilities washing operation typically uses mild conditions and no detergents or strong chemicals. Consequently, any food or product residue constitutes an impurity for the recycling stream. RecyClass encourages testing to verify that the package is “easy-to-empty” and therefore ensures the minimum amount of residual material at the end of its useful life. Nonetheless, this factor is beyond the scope of this Protocol.

## 4. LABORATORY TESTING METHODOLOGY

This methodology aims to reproduce the recycling process at laboratory scale to determine the suitability of an innovation for the PS recycling stream. The methodology described below shall be followed precisely and any modifications or problems during the testing phase must be noted. A Laboratory Evaluation Report compiling objectively all the results obtained shall be prepared to report to the RecyClass Technical Committee (TC) which will interpret the final results. Any remarks during the laboratory tests described in the Protocol shall also be noted down.

---

<sup>6</sup> [Design for Recycling Guidelines](#)

<sup>7</sup> [RecyClass Methodology](#)

# RecyClass

See below in Figure 1 a diagram describing the methodology.

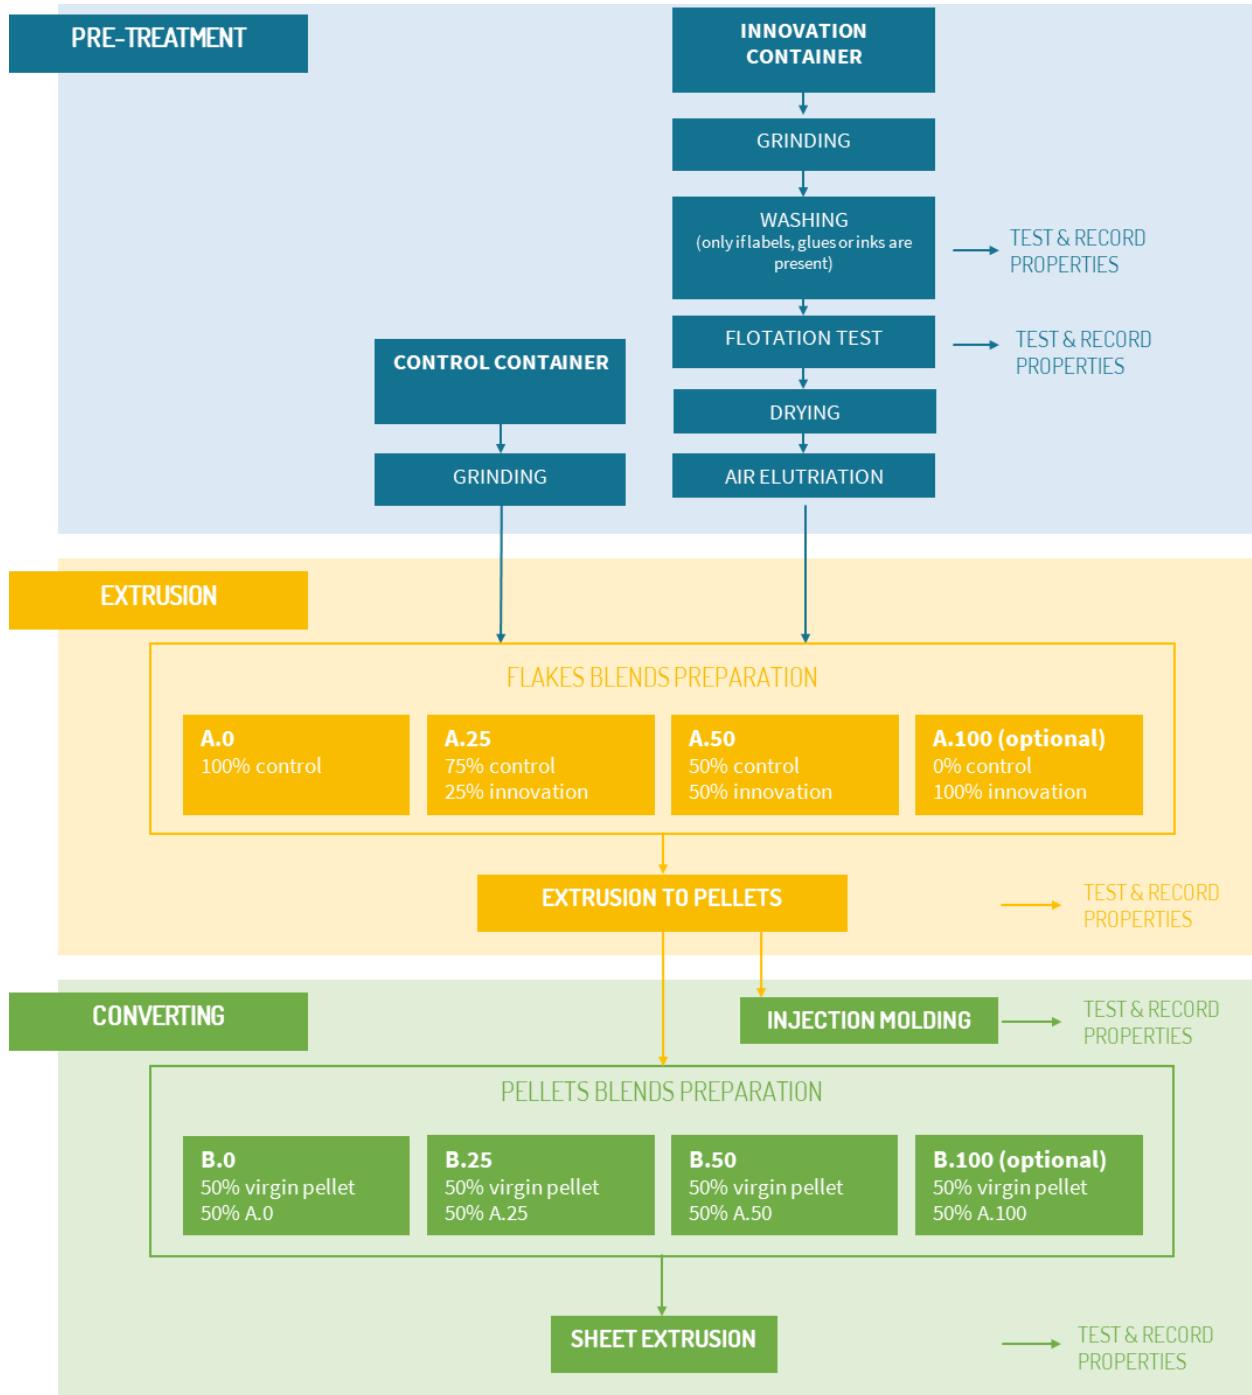


Figure 1. Methodology diagram

# RecyClass

## 4.1 CONTROL SAMPLE SELECTION

The control PS sample for the purpose of performing the Protocol can be selected:

- **Option 1:** If there is a PS container known to be recyclable, consisting of the same base PS virgin materials as the Innovation, except/apart from the specific ingredient/feature being evaluated, it can be selected as the control for this Protocol, with the approval of the RecyClass PS TC.
- **Option 2:** The Applicant can select a PS resin with the same critical technical specifications for MFI and density as the innovation article,  $\pm 0.01$  density can be used as the control for this Protocol, upon the approval of RecyClass PS TC. For MFI, please refer to the Annex 2 table summarizing the MFI range accepted depending on the innovation. A selection of control samples to be used is reported in Annex I. A mixture of the resins listed in Annex 1 reflecting the innovation structure can also be proposed as control, upon the approval of the Technical Committee. The selected material must be extruded at  $230 \pm 10$  °C to obtain the control sample. This step is necessary to realistically represent a material already used as packaging by erasing its previous thermal history.

These options will be used to make both the control flakes and the blends with innovation container flakes that will contain the innovative feature(s) (additive, coating, label, adhesive, multilayer resin, etc.) for the recyclability study.

Since control material is used as reference to evaluate the impact of the innovation, A.0 and B.0 (see Figure 1) need to fulfil some minimum requirements to make the recyclability evaluation valid. RecyClass recognised testing facilities are aware of these minimum requirements and will inform both the Applicant and RecyClass in case of deviations.

For the purpose of the tests the amount of material that the Applicant should provide will depend upon the equipment and scale used in each laboratory. Usually, at least 15 kg of innovation material (as packaging) and 25 kg of control material (as packaging) will be requested to prepare blends of 10 kg. More innovation material could be requested if optional tests are required by the RecyClass PS TC. It is worth pointing out that the protocol should be used to test innovations as specific parts of the packaging, meaning that all the decorations or elements of the packaging do not need to be present. The objective is to evaluate the impact of a specific innovation on the recyclability of HDPE containers. Note that complete packaging (with labels, decoration, closures, etc.) can also be assessed under this present protocol.

## 4.2 VIRGIN SAMPLE SELECTION

The virgin PS sample to be used in this Protocol can be selected from the PS resins listed in the Annex and used as it is (i.e. without applying any thermal pre-treatment).

## 5. LABORATORY TEST PROCEDURES

### 5.1 PRE-TREATMENT STEPS

#### 5.1.1 GRINDING

Control (if provided as container) and innovation samples are separately ground in order to fit the throat of a standard laboratory extruder. In case the control is provided in the form of pellets, only the innovation sample has to be ground. If possible, it is recommended to use a granulator rather than a grinder or shredder.

**Procedure:**

- Report the mass of each sample before grinding as  $m_0$ .
- Grind separately control and innovation samples with a screen containing holes within the range of 10 to 15 mm. Store in separate containers.
- Report the mass of each sample after grinding as  $m_1$  and average flake sizes.

#### 5.1.2 WASHING

Control and innovation PS samples are separately washed to test the impact on wet washing operations. The procedures take care of labels, adhesives, coatings, paper and printing present in the innovation PS container. If none of those are present, go directly to step 5.1.3.

The following procedures must be used for innovation samples only.

**Procedure:**

- Prepare the washing water in a vessel at a 1:4 ratio (5 kg flakes vs 20 l water) with tap water. No added detergents or caustic soda.
- Heat the washing water at 40 °C.
- Wash each sample separately at a 1:4 ratio (5 kg flakes vs 20 l water) at 1000 rpm for 5 minutes.
- Rinse the flakes in a strainer with cold running tap water and stir vigorously for 5 minutes using a manual stirring bar.
- Then drain the material.
- Take photos at each step.

Save the washing and rinsing water separately for visual observation. Record the presence of suspended particles or fibres within the water as well as any water colouration. In the case of presence of adhesives, check and record whether the glue has been diluted after the rinsing or whether remains attached to film flakes. If water colouration is observed, the Bleeding Inks Printed on PS Containers procedures developed by RecyClass can be used to assess these deviations<sup>8</sup>.

#### 5.1.3 SEPARATION BY DENSITY

Following washing, the separation by density test allows flake separation by density, simulating the process of a float/sink tank used in an industrial recycling line. Non-PS components floating together with PS flakes cannot be

---

<sup>8</sup>[RecyClass Quick Test Procedures](#)

# RecyClass

further separated and are extruded with PS. This poses relevant concerns both in the process operations and in the quality of the recyclate, undermining its applications.

The following procedure must be used for innovation samples only.

## Procedure

### STEP 1:

- Homogenise the flakes collected after washing and save 50 g of washed flakes to be used to estimate the efficiency of the density separation.
- Fill a vessel with tap water at a 1:12 ratio (5 kg washed flakes vs 60 l water).
- Add 0.2 wt% of dish detergent.
- Put each sample separately in the water and stir at 750 rpm for 4 minutes.
- Stop the stirrer and allow the water to rest for 10 minutes.
- Remove all the materials that float at the surface with a sieve.
- Take photos of the floating and sinking fractions separately
- Take photos of the water and save it for visual evaluation.

### STEP 2:

- Fill a vessel with tap water at a 1:12 ratio (5 kg sinking fraction of Step 1 vs 60 l water).
- Add 0.2 wt% of dish detergent.
- Add 12 % of sodium chloride to the water solution (or any other salt) to increase the water density up to 1.08 g/cm<sup>3</sup>.
- Put the sank samples from STEP 1 in the water and stir at 750 rpm for 4 minutes.
- Stop the stirrer and allow the water to rest for 10 minutes.
- Recover all the materials that float at the surface with a sieve.
- Rinse the flakes in a strainer with cold running tap water and stir vigorously for 5 minutes using manual stirring bar. Then drain the material.
- Take photos of the floating and sinking fractions separately
- Take photos of the water and save it for visual evaluation.

The test is passed if 100 % of polystyrene material is floating after the 2nd step. It means non-PS material cannot stick or not get separated from PS and cause PS to sink, resulting in yield losses or stay with PS and contaminate the PS stream.

The efficiency of the sink/float separation should be measured using 50 g of washed flakes of innovative samples and a graduated beaker filled with tap water, as described by the following procedure. Repeat the procedure for washed and dried innovation flakes, with and without closure and labels.

## Procedure:

### STEP 1

- Fill a 1 l graduated beaker with 700 ml of tap water (pH between 7 and 8).
- Boil the water for 10 minutes and then cool at room temperature.
- Transfer 300 ml of water to a graduated beaker.
- Add a drop of dish detergent.
- Put the innovative sample in the water and stir at 500 rpm for 4 minutes.
- Stop the stirrer and allow the water to rest for 10 minutes.
- Take photo of the beaker.
- Remove all particles that float on the surface with a sieve.
- Take photos of the floating and sinking fractions separately.
- Save the wash for visual evaluation.

### STEP 2

- Fill a 1 l graduated beaker with 700 ml of tap water (pH between 7 and 8).
- Boil the water for 10 minutes and then cool at room temperature.

# RecyClass

- Transfer 300 ml of water in a graduated beaker.
- Add a drop of dish detergent.
- Add 12 % of sodium chloride to the water solution (or any other salt) to increase the water density up to 1.08 g/cm3.
- Put the sank samples from STEP 1 in the water and stir at 500 rpm for 4 minutes.
- Stop the stirrer and allow the water to rest for 10 minutes.
- Take photo of the beaker.
- Recover all particles that float at the surface with a sieve.
- Rinse the flakes in a strainer with cold running tap water and stir vigorously for 5 minutes using manual stirring bar. Then drain the material.
- Take photos of the floating and sinking fractions separately.
- Save the wash for visual evaluation.
- Dry the floating fraction for 1 hour at 80 °C in a bed desiccant or 3 hours at 65 °C with air.
- Cool to room temperature, weigh and record the weight of the float fraction.
- Repeat the procedure with 50 g of the innovation flakes without caps and labels (if any).
- Calculate the test efficiency as

$$\eta = \frac{W_{F2}}{W_I} \times 100 = \frac{W_I - (W_{S2} + W_{F1})}{W_I} \times 100 [\%]$$

Where:

η: Test efficiency

WF1: weight of floating fraction of step 1

WF2: weight of floating fraction of step 2

WS2: weight of sinking fraction of step 2

WI: weight of innovative sample

## 5.1.4 DRYING

Reduce the flake moisture with ambient air to release surface moisture to less than 1 %.

### Procedure:

- Dry the flakes collected after floatation with air at room temperature without applying vacuum or heat sources until 1 % moisture content is reached. If the moisture content cannot be reached under these conditions, mild heat can be used with prior notification and approval from RecyClass.

## 5.1.5 AIR ELUTRIATION

Control and innovation PS flakes are separately elutriated with air to remove light fraction.

### Procedure:

- As for the second step, elutriate flakes with air with one pass and with less than 2 % loss set for the control flakes.

## 5.2 EXTRUSION

### 5.2.1 FLAKE BLENDS PREPARATION

For each sample obtained, to evaluate and record the properties of innovation PS container against control as laid out in this Protocol, a set of flake blends is prepared as described in Table 1. Blends shall be produced once the control and innovation have separately gone through all pre-treatment steps described above.

# RecyClass

Keep separate the control and innovation flakes obtained following the previous steps, and air dry for 24 hours in an ambient environment. Then, according to the values reported in Table 1 prepare three different blends with 100 % control (and 0 % innovation), 75 % control – 25 % innovation, and 50 % control – 50 % innovation, and tag them respectively as A.0, A.25 and A.50.

For the purpose of the tests the Applicant should provide enough innovation and control materials to allow for the blend preparations (cf. section 4.1.).

## 5.2.2 FLAKE BLENDS COMPOSITION

Three different blends of 0 %, 25 % and 50 % of innovation PS container (optionally 100 % innovation) will be prepared as described in Table 1.

Depending on the application, the TC can also ask the Applicant to perform the tests with a sample of 100 % innovation (i.e. A.100, by replacing the test with A.25).

*Table 1. Flake blends composition for the production of pellets*

BLEND	COMPOSITION	% CONTROL FLAKES	% INNOVATION FLAKES
<b>A.0</b>	100 % Control	100	0
<b>A.25</b>	75 % Control 25 % Innovation	75	25
<b>A.50</b>	50 % Control 50 % Innovation	50	50
<b>OPTIONAL A.100</b>	100 % Innovation	0	100

## 5.2.3 PELLET PRODUCTION

Both control and innovation flakes can be mixed manually before extrusion for blends preparation. The flakes will be dried under the same conditions with a desiccant bed drying unit or with hot air and extruded using a co-rotative twin-screw extruder at a melt temperature of 230 °C. The extrudate will be melt filtered (about 120 µm filtration). Control flake sample A.0 has to be extruded first. Further size reduction before extrusion is acceptable if necessary to allow good feeding of the material into the extruder. Nevertheless, the flake size should be kept constant between all samples. See additional information in Table 2.

The extruder has to be cleaned before starting the extrusion process. This involves pulling the screws out of the barrel and then mechanically cleaning them with brass brushes until they reach a glossy finish. The barrel also has to be mechanically cleaned with round brass brushes from the mandrel to the run-out zone.

*Table 2. Pellet production purpose & overview*

FLAKE COMPOSITIONS	KG OF BLEND REQUIRED	PURPOSE OF BLEND
<b>A.0</b> 100 % Control flake	Per laboratory requirement for a 30-minute run time	All tests compared to control values

# RecyClass

<b>A.25</b> 75 % control with 25 % innovation	Per laboratory requirement for a 30-minute run time	Required for comparison to control values
<b>A.50</b> 50 % control with 50 % innovation	Per laboratory requirement for a 30-minute run time	Required for comparison to control values
<b>OPTIONAL</b> <b>A.100</b> 100 % innovation	Per laboratory requirement for a 30-minute run time	Optional, to evaluate the impact of higher concentration of innovation on recycling.

#### Procedure:

- Dry samples A.0, A.25 and A.50 (optionally A.100) with a bed desiccant for 1 hour at 80 °C or with hot air at 80 °C for 1 hour.
- Extrude first the sample A.0 (the control blend) at a melt temperature of  $230 \pm 10$  °C and with a 120 µm melt filter pack, for no less than 30 minutes. Melt residence time should be less than 6 minutes.
- Recommended throughput is between 5 and 10 kg/h and rotation speed between 100 and 200 rpm.
- Monitor the extrusion process for heat stability.
- Rapidly cool the extrudate in a water bath and feed it into a pelletiser.
- The pelletizer speed has to be controlled to get a final pellet with a diameter of 3 mm.
- Monitor pressure build-up during pelletizing and report significant differences.
- Randomly select the pellets to perform all the characterisations reported in Table 3.
- Change the melt filter pack between samples for visual examination.
- Be sure to produce enough pellets for all the tests, including the conversion tests.

Record the resulting properties in Table 3. The processing conditions used for all the samples must be identical. If some operating conditions need to be modified for A.25 and A.50 (optionally A.100) samples, this information must be documented in the report. A small amount of each sample (50 g) will be retained for the RecyClass TC and the Applicant. The extruded pellets will be tested for pellet properties characterisation (Table 3). The pellets of the test samples will be compared with the pellets of the control sample. All pellets should meet the requirements reported in Table 3.

If filterability is seen as a potential problem for the innovative samples, a dedicated filter test should be requested by the RecyClass PS TC.

#### 5.2.3.1 FILTRATION TEST (OPTIONAL)

Filter contamination problems may occur when one of the components in the innovation sample is causing gels, larger particles, or releases degraded particles. Pressure drop must be monitored during pelletising since a pressure increase is an indication of the risk of filter contamination. If from previous step, the monitoring of pressure-drop and the visual inspection of the filter after the pelletisation induce to further analyse contamination, a dedicated filtration test should be done. To limit the test duration, the innovation sample will not be mixed with control PS.

About 5 kg of pellets from the pure control PS and the pure innovation PS samples will be separately extruded for a minimum of 30 minutes and filtered using a 120 µm screen pack. The 100 % control sample must be extruded first.

#### Procedure:

- Dry the control sample before extrusion with a bed desiccant for 1 hour at 80 °C or with hot air at 80 °C for 1 hour.
- Extrude the sample at a temperature of  $230 \pm 10$  °C and with a 120 µm melt filter pack, for no less than 30 minutes.

# RecyClass

- If required, small changes in the process parameters are admitted keeping the extrusion stable over the time but must be recorded. However, continuous adjustments of the operating parameters during the runs to overcome steady-state conditions are not admitted.
- Monitor the pressure drop during the test and register variations.
- Repeat the procedure for the innovation sample with the identical operating parameters used for the control sample filtration.

The test is passed if the pressure before the filter does not double from the starting pressure during or at the end of the analysis.

## 5.2.3.2 EXTRUSION PROCESS OBSERVATIONS

*Table 3. Extrusion process observations & monitoring*

ASSESSMENT	STANDARD	BENCHMARK RECOMMENDATION
Odours	<b>0:</b> No noticeable odours, even right next to the extruder. <b>1:</b> Slight odour near the extruder, noticeable but not a problem for operators. <b>2:</b> Strong odour in the work area, sometimes needing ventilation, but still manageable. <b>3:</b> Very strong odour, making it uncomfortable, forcing operators to move away from the extruder or use protective equipment	0 or 1  If odours present, report more details  Report with pictures in comparison with A.0
Fumes	<b>0:</b> No visible fumes observed near the extruder. <b>1:</b> Slight fumes observed, disappearing quickly. <b>2:</b> Moderate fumes, clearly visible and staying in the air for some time. <b>3:</b> Heavy fumes, very visible and dense, making it hard for operators to stay near the extruder.	0 or 1  If 2 or 3, report with pictures  Report with pictures in comparison with A.0
Die build-ups	<b>0:</b> No dye build-ups observed. <b>1:</b> Minor dye build-ups observed. <b>2:</b> Frequent dye build-ups, clearly visible. <b>3:</b> Significant dye build-ups, preventing proper strand formation.  Visual inspection. In case of presence of build-ups, an FTIR analysis is recommended to identify the origin of the deposit.	0 or 1  If 2 or 3, report with pictures  Report with pictures in comparison with A.0
Average Pressure (MPa)	Average pressure after extruding through 120 µm filter for the stable 15-minute run time, compared to 100 % control	No more than a 25 % increase to A.0
Pressure Variation (MPa)	(P <sub>25-30 minutes</sub> - P <sub>5 first minutes</sub> )	No increase higher than 25 % compared to start

### 5.2.3.3 PELLET PROPERTIES EVALUATION

Samples preparation and testing conditions of PS pellets for the following characterisations must be done according to ISO 24022-2:2020 Polystyrene (PS) moulding and extrusion materials, Part 2: Preparation of test specimens and determination of properties.

*Table 4. Pellet properties evaluation*

ASSESSMENT	STANDARD	BENCHMARK RECOMMENDATION
Bulk Density (kg/m <sup>3</sup> )	ISO 60	Record
Density (kg/m <sup>3</sup> )	ISO 1183-1	Between 1 and 1.08 g/cm <sup>3</sup>
Melt Index (g/10 min)	ISO 1133-1 (200 °C/5 kg)	Between 3 and 9 g/10 min
Ash content (wt%)	ISO 3451-1	A.25, A.50 and A.100 respectively lower than 1.5, 3 and 5 wt%
Filtration (µm)	Visual inspection	No build-up on the screen
Moisture (wt%)	Moisture analyser	<0.1 wt%
Impurities	Visual inspection	Record
Surface appearance	Visual inspection	Record
Volatiles (wt%)	10 g air-dried pellets exposed to 200 °C for 10 minutes	± 0.1wt% for A.25 and A.50 respect to A.0
Average Pressure (MPa)	Average Pressure it after extruding through 120 µm for the stable 30 minutes run time, compared to 100 % control	No more than a 10 % delta increase to A.0
Pressure Variation (MPa)	(P <sub>5</sub> last minutes - P <sub>5</sub> first minutes)	No increase higher than 25 % compared to start in 30 minutes
Extrusion process	Unusual sticking, fumes, odour, and any build-up	Record

### 5.3 CONVERTING

Since the Protocol aims to assess the highest value recyclate application, injection moulding and sheet extrusion will be a priority. In any case, three blends of innovation and control pellets will be produced aiming to assess different innovation concentration in the recycling stream, as following reported.

#### 5.3.1 INJECTION MOULDING

Pellets A.0, A.25 and A.50 (optionally A.100) must be tested for injection moulding to evaluate tensile properties, colours, as well as defects.

Control pellets A.0 must be moulded first.

# RecyClass

## Procedure:

- Dry the samples A.0, A.25 and A.50 (optional: A.100) at 75 °C for 2 hours.
- Mould sample A.0 at 210-250 °C to multipurpose specimens' type 1A according to EN ISO 527-2 and to plaques with measures of about 60 x 60 x 2 mm<sup>3</sup>.
- The run time is variable but should be not less than 30 minutes. The specimens should be completely filled without any shrinkage, overspray, or inclusions.
- Samples A.25 and A.50 (optionally A.100) must be moulded following the identical operating conditions of the control sample A.0.
- Tag the plaques produced with A.0, A.25 and A.50 (optionally A.100) as C.0, C.25 and C.50 (optionally C.100), respectively.
- Small variations in operating conditions could be acceptable but must be documented in the report.
- For each material monitor the heat stability and the injection pressure.

Record the resulting properties in Table 5. Mechanical data must be analysed on the 1A specimen, while colour, inclusions, and surface should be analysed on the plaque. If some operating conditions need to be modified for A.25 and A.50 (optionally A.100) samples, this information must be documented in the report.

### 5.3.1.1 INJECTION MOULDED PARTS PROPERTIES EVALUATION

Samples preparation and testing conditions of PS samples for the following characterisations must be done according to ISO 24022-2:2020 Polystyrene (PS) moulding and extrusion materials, Part 2: Preparation of test specimens and determination of properties.

*Table 5. Injection moulded parts properties evaluation*

ASSESSMENT	STANDARD	BENCHMARK RECOMMENDATION
Flexural modulus (MPa)	ISO 178	No more than 10 % delta decrease compared to A.0
Tensile Strength at Yield (%)	ISO 527	No more than 25 % delta decrease compared to A.0
Tensile Stress at Break (MPa)	ISO 527	No more than 25 % delta decrease compared to A.0
Charpy impact test strength (kJ/m <sup>2</sup> )	ISO 179-1	No more than 10 % delta decrease compared to A.0
Reflection Colour	(L*, a*, b*)	Record
Surface Appearance	Visual inspection	No black specks
Inclusions of extraneous material	Visual inspection	Record

### 5.3.2 SHEET EXTRUSION

#### 5.3.2.1 PELLET BLENDS PREPARATION

Once PS pellets have been produced and tested, three additional blends of 50 % virgin – 50 % blend A shall be produced for the converting tests. Keep separated the pellet samples previously produced and dry them for 10 minutes at 60 °C.

# RecyClass

Then according to the values reported in Table 6, prepare three different blends with 0 % innovation (50 % virgin and 50 % A.0 pellets), 12.5% innovation (50 % virgin and 50 % A.25 pellets), and 25 % innovation (50 % virgin and 50 % A.50 pellets), and tag them as samples B.0, B.25 and B.50 respectively.

Eventually, depending on the application and its market penetration, the TC can ask the Applicant to also perform the tests with a sample of 50 % innovation (i.e. B.100, by replacing the test with B.25).

## 5.3.2.2 PELLET BLENDS COMPOSITION

Three different blends at 50 % virgin pellet – 50 % Blend A shall be produced as described in Table 6. Blends will be composed of 0 %, 12.5% and 25 % content (eventually ending at 50 %) based on the weight of the initial innovation PS container.

*Table 6. Pellet blends composition for the application tests*

BLEND	COMPOSITION	% VIRGIN RESIN	EFFECTIVE % CONTROL	EFFECTIVE % INNOVATION
<b>B.0</b>	50 % Virgin Pellet 50 % A.0	50	50	0
<b>B.25</b>	50 % Virgin Pellet 50 % A.25	50	37.5	12.5
<b>B.50</b>	50 % Virgin Pellet 50 % A.50	50	25	25
<b>OPTIONAL B.100</b>	50 % Virgin Pellet 50 % A.100	50	0	50

The Applicant must submit its innovation primarily to sheet extrusion to test the recyclate obtained by the innovation in a closed-loop application.

Control pellet blend B.0 must be extruded first.

### Procedure:

- Dry samples B.0, B.25 and B.50 (optionally B.100) at 60 °C for 10 minutes.
- Extrude sheets at melt temperature of  $230 \pm 10$  °C with thickness of 800 µm under conditions determined for the control sample B.0. Temperature of the rollers should be set with the B.0 blend and same conditions must be used for the innovation blends
- Extrusion run time per variable, no less than 30 minutes.
- Samples B.25 and B.50 (optionally B.100) must be extruded following the identical operating conditions of the control sample B.0.
- Small variations in operating conditions could be acceptable but must be documented in the report.

Record the resulting properties in Samples preparation and testing conditions of PS samples for the following characterisations must be done according to ISO 24022-2:2020 Polystyrene (PS) moulding and extrusion materials, Part 2: Preparation of test specimens and determination of properties.

Table 7. If some operating conditions needed to be modified for B.25 and B.50 samples, this information must be documented in the report.

# RecyClass

## 5.3.2.3 SHEET PROPERTIES CHARACTERISATION

Samples preparation and testing conditions of PS samples for the following characterisations must be done according to ISO 24022-2:2020 Polystyrene (PS) moulding and extrusion materials, Part 2: Preparation of test specimens and determination of properties.

*Table 7. Sheet properties evaluation*

ASSESSMENT	STANDARDS	BENCHMARK RECOMMENDATION
Thickness		Variations lower than 3 %
Tensile Modulus (MPa)	ISO 527-3	No more than a 10 % delta decrease to B.0
Tensile Stress at Yield (TD*) (MPa)		
Tensile Stress at Yield (MD**) (MPa)	ISO 527-3	No more than a 25 % delta decrease to B.0
Tensile Stress at Break (TD*) (MPa)		
Tensile Stress at Break (MD**) (MPa)		
Colour	Visual inspection	No discolouration
Surface Appearance	Visual inspection	No black specks
Fisheyes	Visual inspection	Record the amount and size distribution per m <sup>2</sup> . No fisheyes should be bigger than 1 mm <sup>2</sup> .
Inclusions of extraneous material	Visual inspection	Record

\*TD: transverse direction

\*\*MD: machine direction

## DOCUMENT VERSION HISTORY

VERSION	PUBLICATION DATE	REVISION NOTES
1.0	February 2022	Recyclability Evaluation Protocol for PS Containers release
1.1	August 2022	Mandatory washing and floatation step for control sample removed Wording for sample quantity requested for testing Temperature for extrusion now specific to melt-temperature
2.0	January 2023	Modification of option 2 for control selection Modification of the water/flake ratio, resting time and rinsing for the separation by density step Mild conditions accepted for drying Temperature and procedure for extrusion and injection modified
3.0	January 2024	Clarification on the units' system to be used Addition of ISO 24022-2:2020 for characterization of PS samples Correction of typos and revised wording
4.0	January 2025	Revision of flotation step Correction of typos Clarification on grinding sieve size Addition of a table to characterise the extrusion process Revised wording Peer reviewed version
4.1.0	February 2026	Clarification on rollers temperature during sheet extrusion. Clarification on ash content and moisture measurements. Correction of typos.

# RecyClass

Identification of versions

v.X - Structural modification impacting the protocol.

v.X.Y – Updates to testing conditions, integration of new tests, technologies or analytical methods.

v.X.Y.Z - Editorial modifications not impacting the content of the Protocol.

## ANNEX I – CONTROL SAMPLES SELECTION

Type of PS	PS	Density, g/cm <sup>3</sup>	MFI, g/10min (200 °C/5 kg)
GPPS	Styrolution Taxed 1050	1.04	2.8
GPPS	Styron™ 660	1.04	7.0
GPPS	EDISTIR® N3560	1.05	3.8
GPPS	EDISTIR® N3840	1.05	10
HIPS	STYRON™ C-TECH	1.04	6.3
HIPS	Styrolution PS 476L	1.05	5.5
HIPS	EDISTIR® R850E	1.04	4

## ANNEX 2 – MFI RANGE FOR CONTROL SAMPLE (OPTION 2)

<b>MFI of PS grade in innovation (g/10min, 190 °C, 2.16 kg)</b>	<b>Range of MFI accepted for control selection (g/10min, 190 °C, 2.16 kg)</b>
<4	± 1 compared to PS present in innovation
Between 4 and 8.5	± 2 compared to PS present in innovation
Between 8.5 and 15	± 3 compared to PS present in innovation
>15	± 5 compared to PS present in innovation

# RecyClass

Avenue de Broqueville 12  
1150 Brussels – Belgium

Phone: +32 2 786 39 08  
[info@recyclass.eu](mailto:info@recyclass.eu)

[www.recyclass.eu](http://www.recyclass.eu)